

# Green synthesis of silver nanoparticles in aloe vera plant extract prepared by a hydrothermal method and their synergistic antibacterial activity

Patcharaporn Tippayawat<sup>Corresp., 1, 2</sup>, Nutthakritta Phromviyo<sup>3</sup>, Parichart Boueroy<sup>4</sup>, Apiwat Chompoosor<sup>5, 6</sup>

<sup>1</sup> Division of Clinical Microbiology/ Faculty of Associated Medical Sciences, Khon Kaen University, Khon Kaen, Thailand

<sup>2</sup> The Center for Research & Development of Medical Diagnostic Laboratories/ Faculty of Associated Medical Sciences, Khon Kaen University, Khon Kaen, Thailand

<sup>3</sup> Materials Science and Nanotechnology Program/ Faculty of Science, Khon Kaen University, Khon Kaen, Thailand

<sup>4</sup> Department of Microbiology/ Faculty of Medicine, Khon Kaen University, Khon Kaen, Thailand

<sup>5</sup> Department of Chemistry/ Faculty of Science, Ramkhamhaeng University, Bangkok, Thailand

<sup>6</sup> Integrated Nanotechnology Research Center (INRC), Khon Kaen University, Khon Kaen, Thailand

Corresponding Author: Patcharaporn Tippayawat

Email address: patchatip@kku.ac.th

**Background:** There is worldwide interest in silver nanoparticles (AgNPs) synthesized by various chemical reactions for use in applications exploiting their antibacterial activity, even though these processes exhibit a broad range of toxicity in vertebrates and invertebrates alike. To avoid the chemical toxicity, biosynthesis (green synthesis) of metal nanoparticles is proposed as a cost-effective and environmental friendly alternative. Aloe vera leaf extract is a medicinal agent with multiple properties including an antibacterial effect. Moreover the constituents of aloe vera leaves include lignin, hemicellulose, and pectins which can be used in the reduction of silver ions to produce as AgNPs@aloe vera (AgNPs@AV) with antibacterial activity. **Methods:** AgNPs were prepared by an eco-friendly hydrothermal method using an aloe vera plant extract solution as both a reducing and stabilizing agent. AgNPs@AV were characterized using XRD and SEM. Additionally, an agar well diffusion method was used to screen for antimicrobial activity. MIC and MBC were used to correlate the concentration of AgNPs@AV its bactericidal effect. SEM was used to investigate bacterial inactivation. Then the toxicity with human cells was investigated using an MTT assay. **Results:** The synthesized AgNPs were crystalline with sizes of  $70.70 \pm 22$ - $192.02 \pm 53$  nm as revealed using XRD and SEM. The sizes of AgNPs can be varied through alteration of times and temperatures used in their synthesis. These AgNPs were investigated for potential use as an antibacterial agent to inhibit pathogenic bacteria. Their antibacterial activity was tested on *S. epidermidis* and *P. aeruginosa*. The results showed that AgNPs had a high antibacterial which depended on their synthesis conditions, particularly when processed at 100 °C for 6 h and 200 °C for 12 h. The cytotoxicity of AgNPs was determined using human PBMCs revealing no obvious cytotoxicity. These

results indicated that AgNPs@AV can be effectively utilized in pharmaceutical, biotechnological and biomedical applications. **Discussion:** Aloe vera extract was processed using a green and facile method. This was a hydrothermal method to reduce silver nitrate to AgNPs@AV. Varying the hydrothermal temperature provided the fine spherical shaped nanoparticles. The size of the nanomaterial was affected by its thermal preparation. The particle size of AgNPs could be tuned by varying both time and temperature. A process using a pure AG phase could go to completion in 6h at 200 °C, whereas reactions at lower temperatures required longer times. Moreover, the antibacterial effect of this hybrid nanomaterial was sufficient that it could be used to inhibit pathogenic bacteria since silver release was dependent upon its particle size. The high activity of the largest AgNPs might have resulted from a high concentration of aloe vera compounds incorporated into the AgNPs during hydrothermal synthesis.

# **Green synthesis of silver nanoparticles in aloe vera plant extract prepared by a hydrothermal method and their synergistic antibacterial activity**

Pacharaporn Tippayawat<sup>1,2\*</sup>, Nutthakritta Phromviyo<sup>3</sup>, Parichart Boueroy<sup>4</sup>, Apiwat Chompoosor<sup>5,6\*</sup>

<sup>1</sup>Division of Clinical Microbiology, Faculty of Associated Medical Sciences, Khon Kaen University, Khon Kaen, 40002, Thailand

<sup>2</sup>The Center for Research & Development of Medical Diagnostic Laboratories, Faculty of Associated Medical Sciences, Khon Kaen University, Khon Kaen, Thailand

<sup>3</sup>Materials Science and Nanotechnology Program, Faculty of Science, Khon Kaen University, Khon Kaen, 40002, Thailand

<sup>4</sup>Department of Microbiology, Faculty of Medicine, Khon Kaen University, Khon Kaen, 40002, Thailand

<sup>5</sup>Department of Chemistry, Faculty of Science, Ramkhamhaeng University, Ramkhamhaeng Road, Huamark, Bangkok, Bangkok, 10240, Thailand

<sup>6</sup>Integrated Nanotechnology Research Center (INRC), Khon Kaen University, Khon Kaen, 40002, Thailand

Corresponding authors:

Pacharaporn Tippayawat<sup>1,2</sup>

Department of Clinical Microbiology, AMS, Khon Kaen University, 123 Mittrapharb Road, Muang, Khon Kaen, Thailand, 40002

Email address: patchatip@kku.ac.th

Apiwat Chompoosor<sup>5,6</sup>

Department of Chemistry, Faculty of Science, Ramkhamhaeng University, Ramkhamhaeng Road, Huamark, Bangkok, Bangkok, Thailand, 10240

Email address: apiwat@ru.ac.th

26

## 27 **Abstract**

28 **Background:** There is worldwide interest in silver nanoparticles (AgNPs) synthesized by various  
 29 chemical reactions for use in applications exploiting their antibacterial activity, even though these  
 30 processes exhibit a broad range of toxicity in vertebrates and invertebrates alike. To avoid the  
 31 chemical toxicity, biosynthesis (green synthesis) of metal nanoparticles is proposed as a cost-  
 32 effective and environmental friendly alternative. Aloe vera leaf extract is a medicinal agent with  
 33 multiple properties including an antibacterial effect. Moreover the constituents of aloe vera leaves  
 34 include lignin, hemicellulose, and pectins which can be used in the reduction of silver ions to  
 35 produce as AgNPs@aloe vera (AgNPs@AV) with antibacterial activity.

36 **Methods:** AgNPs were prepared by an eco-friendly hydrothermal method using an aloe vera plant  
 37 extract solution as both a reducing and stabilizing agent. AgNPs@AV were characterized using  
 38 XRD and SEM. Additionally, an agar well diffusion method was used to screen for antimicrobial  
 39 activity. MIC and MBC were used to correlate the concentration of AgNPs@AV its bactericidal  
 40 effect. SEM was used to investigate bacterial inactivation. Then the toxicity with human cells was  
 41 investigated using an MTT assay.

42 **Results:** The synthesized AgNPs were crystalline with sizes of  $70.70 \pm 22$ - $192.02 \pm 53$  nm as  
 43 revealed using XRD and SEM. The sizes of AgNPs can be varied through alteration of times and  
 44 temperatures used in their synthesis. These AgNPs were investigated for potential use as an  
 45 antibacterial agent to inhibit pathogenic bacteria. Their antibacterial activity was tested on *S.*  
 46 *epidermidis* and *P. aeruginosa*. The results showed that AgNPs had a high antibacterial which  
 47 depended on their synthesis conditions, particularly when processed at 100 °C for 6 h and 200 °C  
 48 for 12 h. The cytotoxicity of AgNPs was determined using human PBMCs revealing no obvious

cytotoxicity. These results indicated that AgNPs@AV can be effectively utilized in pharmaceutical, biotechnological and biomedical applications.

**Discussion:** Aloe vera extract was processed using a green and facile method. This was a hydrothermal method to reduce silver nitrate to AgNPs@AV. Varying the hydrothermal temperature provided the fine spherical shaped nanoparticles. The size of the nanomaterial was affected by its thermal preparation. The particle size of AgNPs could be tuned by varying both time and temperature. A process using a pure AG phase could go to completion in 6 h at 200 °C, whereas reactions at lower temperatures required longer times. Moreover, the antibacterial effect of this hybrid nanomaterial was sufficient that it could be used to inhibit pathogenic bacteria since silver release was dependent upon its particle size. The high activity of the largest AgNPs might have resulted from a high concentration of aloe vera compounds incorporated into the AgNPs during hydrothermal synthesis.

## Introduction

Silver nanoparticles (AgNPs) have been extensively studied for many decades due to their unique features and wide range of applications. Their uses include catalysis (*Pradhan, Pal & Pal, 2002*), biosensing (*Anker et al., 2008*), imaging (*Lee & El-Sayed, 2006*), and antibacterial activity (*Morones et al., 2005; Rai, Yadav & Gade, 2009*). Among these applications, antibacterial activities have gained much attention because they potentially offer a solution to the problem of antibiotic resistance (*Cho et al., 2005*). There are a variety of methods to synthesize AgNPs including physical and chemical methods (*Chudasama et al., 2010*). Chemical reduction of silver ions using sodium borohydride (*Zhang et al., 2000*), hydrazine (*Taleb, Petit & Pileni, 1997*), ascorbic acid (*Lee et al., 2004*), trisodium citrate (*Sun Mayers & Xia, 2003*), and polyols (*Sun &*

*Xia, 2002*) were reported and are considered well-established methods. Although chemical routes are effective, these methods may suffer from toxicity due to the chemicals used and the difficulty in removing them. Additionally, chemical reagents used in these methods are hazardous to the environment (*Nabikhan et al., 2010*). To avoid the toxicity of chemicals, green synthesis was developed (*Sharma, Yngard & Lin, 2009*). This method of biosynthesis of metal nanoparticles has been proposed as a cost-effective and environmental friendly way of fabricating these materials. Synthesis of AgNPs employing either microorganisms or plant extracts has emerged as an alternative approach. These biosynthetic methods have a numbers of benefits. They are simple, cost-effective, give high yields, and are environmentally friendly (*Zhang et al., 2013*). Plant extracts have reportedly been used in the preparation of AgNPs (*Sun et al., 2014*). Aloe vera leaves have been used as medicinal plants since they possess anti-inflammatory activity, UV protection, anti-arthritic properties, promote wound and burn-healing, and have antibacterial properties (*Chandran et al., 2006; Feng et al., 2000; Reynolds & Dweck, 1999; Vazquez et al., 1996*). There are a number of biologically active constituents in aloe vera leaves. These include lignin, hemicellulose, pectins which can be used in the reduction of silver ions (*Emaga et al., 2008*). It is believed that the large enzymes and proteins in aloe vera extract are weakly bound to silver ions and function as a complexing agent. Due to their low cost and environmentally friendly nature coupled with their reducing properties, we selected aloe vera as the reducing and stabilizing agent to prepare AgNPs and test their antibacterial activity.

In this study, we report a one-step hydrothermal method to prepare silver nanoparticles. Reduction of  $\text{Ag}^+$  ions to  $\text{Ag}^0$  nanoparticles was done in a medium of aloe vera extract in which no extra reducing agent was used. The resulting AgNPs can be obtained in large quantities. The sizes of AgNPs were found to be in a range of 70.70-192.02 nm and controllable by varying temperature

and time conditions of the hydrothermal process. Further, the resulting AgNPs were found to be effective against gram-positive (*Streptococcus epidermidis*) and gram-negative (*Pseudomonas aeruginosa*). Therefore, this work has shown the use of naturally occurring compounds to be a reducing and stabilizing agent. This method is considered green synthesis. The resulting silver nanoparticles showed a synergism of aloe vera and silver nanoparticles on bactericidal effect. This hybrid nanomaterial provides an alternative material for using in antibacterials.

## Materials and Methods

In this study, silver nitrate, AgNO<sub>3</sub> (Sigma-Aldrich Chemicals, USA) and aloe vera plant extract were used as the starting materials. The aloe vera extract solution was prepared using 50 g of aloe vera leaves that had been rinsed with deionized water and finely cut into small pieces. The chopped aloe vera leaves were boiled in a 50 mL of deionized water for 20 minutes and allowed to cool. The cooled leaf broth was filtered and stored in a refrigerator at 4 °C. The resulting extract was used as an aloe vera extract solution.

## Synthesis of AgNPs and Characterization of AgNPs

In the preparation of AgNPs samples, AgNO<sub>3</sub> (0.3 mol) was first dissolved in 20 ml of deionized water and mixed with 20 ml of aloe vera extract solution under vigorous stirring at room temperature for 30 minutes. The mixtures were added to sealed Teflon-lined vessels of 100 mL capacity (Parr, USA), which were heated and maintained at various time and temperature conditions, and then gradually cooled to room temperature. A gray precipitate was collected by filtration and washed with deionized water several times, and finally dried in air at 60 °C for 6 h. The crystal phase analysis of the AgNPs powders was conducted using X-ray diffraction (XRD) (PW3710, the Netherlands) with CuKα radiation ( $\lambda = 0.15406$  nm). The particle sizes and

morphology of the prepared AgNPs samples were characterized using scanning electron microscopy (SEM) (LEO SEM 1450VP, UK) and transmission electron microscopy (TEM) (FEI 5022/22 Tecnai G2 20 S-Twin, CR). The UV–visible absorbance of the AgNPs was measured using UV-1800 (Shimadzu, Japan).

## **Antibacterial Tests and Cytotoxicity Test**

### **Well diffusion method**

The antibacterial activity of AgNPs prepared under different hydrothermal processing conditions were tested against gram-negative *P. aeruginosa* (*Pseudomonas aeruginosa*, ATCC27803) and gram-positive *S. epidermidis* (*Staphylococcus epidermidis*, ATCC35984) using an agar well diffusion method. The organisms were sub-cultured in nutrient broth at 37 °C and incubated overnight. After that, Nutrient Agar (Merck) was swabbed with the respective sub-cultures ( $1 \times 10^8$  CFU/ml). Specimens containing AgNPs were then arranged on the swabbed agar surface and incubated at 37 °C for 24 h. The results were read by measuring the diameter of the inhibition zone (mm). The experiments were done in triplicate.

### **Scanning electron microscopy (SEM)**

Scanning electron microscopy of control cells and AgNPs treated cells (0.04 mg/mL) was performed to investigate the antibacterial activity. Each bacterial culture was prepared as described above and then pipetted into a 6-well plate with and without AgNPs prior to covering the wells with glass slides. After incubating at 37 °C overnight, the glass slides were removed and gently washed with phosphate buffer saline 3 times before dehydration in an alcohol series using concentrations of 25%, 50%, 75%, 90% and 100% ethanol in distilled water. The slides were left



in each concentration for 20 minutes. They were then air dried and kept in a desiccator until analysis.

### **Minimum inhibitory concentration (MIC) and minimal bactericidal concentration (MBC)**

A microdilution method was used to indicate the bactericidal effect of AgNPs. A suspension of  $1 \times 10^8$  CFU/ml of bacteria in nutrient broth was prepared as described above. The antibacterial solutions were prepared using serial two-fold (1:2) dilutions of AgNPs in concentrations ranging from 0.04 to 0.00008 mg/mL and incubated at 37 °C for 24 h. In the range of sample turbidity, the MIC of the samples could not be determined to identify the lowest concentration of antibacterial agent that inhibits 99% of the growth of the bacteria. A microdilution measurement was done in triplicate to confirm the value of MIC for each tested bacteria. As such, the MBC was measured after MIC determination. In this assay, 10 µl from all concentrations of AgNPs were pipetted onto nutrient agar plates and incubated at 37 °C for 24 h. The MBC endpoint was interpreted at the lowest concentration of antibacterial agent killing 100% of the initial bacterial population.

### **Cytotoxicity Test**

The AgNP samples produced at 100 °C for 6 h and 200 °C for 12 h were tested for their cytotoxicity using the MTT (3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide) assay. Human peripheral blood mononuclear cells (PBMCs) from the leftover buffy coat were suspended into complete 1640 RPMI (supplemented with 10% fetal bovine serum, 2 mM L-glutamine, 100 unit/ml penicillin and 100 µg/ml streptomycin) in a 96-well plate at a density of  $10^5$  cells/well. This was done prior to exposure to AgNPs dissolved in RPMI to make a stock concentration at 0.04 mg/mL. The stock solution was used to generate serial two-fold dilution at 4 concentrations, i.e., 0.02, 0.01, 0.005, and 0.0025 mg/mL. Then, the cells were incubated at 37 °C in a fully humidified, 5% CO<sub>2</sub> air atmosphere for 48 h. The test samples were removed from the cell cultures and the cells were

reincubated for a further 24 h in fresh medium. They were then tested using the MTT assay. Briefly, 50  $\mu$ l of MTT in phosphate buffered saline at 5 mg/ml was added into a medium in each well and the cells were incubated for 4 h. The medium and MTT were then gently aspirated from the wells and solubilized in formazan with 200  $\mu$ l of DMSO and 25  $\mu$ l of Sorensen's Glycine buffer, pH 10.5. The optical density was read with a microplate reader at a wavelength of 560 nm. The average of 3 wells was used to determine the mean of each point. Then % survival of the cells was calculated. For each test sample, the data was used to determine the concentration of sample required to kill 50% ( $IC_{50}$ ) of the cells compared to that of the controls. A dose-response curve was derived from 5 concentrations in the test range using 3 wells per concentration.

## Results

### Characterization of Silver Nanoparticles

The morphology of AgNPs prepared at different reaction temperatures and times was examined using SEM. The result showed SEM images of AgNPs obtained by the reduction of  $AgNO_3$  with aloe vera plant extract (Fig. 1). It was found that the reaction time and temperature had significant effects on the formation of Ag nanostructures. AgNPs were observed as spherical particles with the sizes between 70.7-192.02 nm, moreover the sizes of the materials were significantly affected by their preparation temperature as presented in Table 1. At 6 h, the AgNPs showed the sizes of  $70.70 \pm 23$ ,  $79.47 \pm 22$ , and  $161.66 \pm 53$  nm prepared at 100  $^{\circ}C$ , 150  $^{\circ}C$  and 200  $^{\circ}C$ , respectively. At 12 h, the AgNPs showed sizes of  $95.25 \pm 23$ ,  $149.55 \pm 47$  and  $192.02 \pm 53$  nm prepared at 100  $^{\circ}C$ , 150  $^{\circ}C$  and 200  $^{\circ}C$ , respectively. Furthermore, TEM image of AgNPs prepared at 100  $^{\circ}C$  for 6 h indicating that the size of AgNPs was in good agreement with SEM results, UV-vis absorption spectra of AgNPs showed that the maximum absorption was found at 420 nm and was attributed

to the surface plasmon resonance of AgNPs (Figs. 2A and 2B). The XRD patterns of AgNPs resulted from using the above 3 hydrothermal conditions (Figs. 3A and 3B). All of the main peaks were indexed as AgNPs with the face centered cubic (fcc) lattice of silver, as shown in the standard data (JCPDS file No.01-071-4613). The diffraction peaks at  $2\theta$  degree of 38.2, 44.3, 64.5 and 77.1 corresponded to the (111), (200), (220), and (311) planes, respectively. A pure phase of Ag was only obtained at a temperature of 200 °C for 6 h. The chemical reaction to form a pure phase at 100 and 150 °C for 6 h was incomplete because reaction at such a low temperature usually requires a longer time (Fig. 3A). The existence of Ag<sub>2</sub>O was shown at the peak at around 31.9 (Liu *et al.*, 2010). The result showed a pure Ag phase in all the samples prepared using hydrothermal conditions for 12 h (Fig. 3B).

# Antibacterial Effects

An advantage of silver nanoparticles is that they are known to have an antibacterial effect (Rai *et al.*, 2012). However, the AgNPs formed during the aloe vera hydrothermal method, AgNPs@AV, need to have bioactive functions. It is especially important to understand the functional effects on microorganisms in order to develop novel antibacterial agents. To demonstrate this activity, AgNPs were studied for their bactericidal effect against pathogenic gram-positive *S. epidermidis* and gram-negative *P. aeruginosa*. These two strains are the opportunistic bacteria causing of nosocomial infection, moreover there are the virulent factors involving with antibiotic resistance (Otto 2009; Livermore 2002). Thus, our new product might be a material of choice to apply in antimicrobial activity instead of antibiotics. This was done using a qualitative antibacterial well diffusion assay and studying AgNPs interaction with bacteria using SEM. Quantitative antibacterial concentrations were evaluated by determining the minimum bactericidal concentration (MBC). It was observed that the inhibition zones of both pathogens were significant

for 0.1 mg/mL AgNPs prepared at 100 °C for 6 h, 150 °C and 200 °C for 12 h compared with the control (Fig. 4 and Table 1). The AgNPs synthesized under different conditions provided varying bactericidal effects. Then, the effects of two AgNPs@AV samples including those prepared at 100 °C for 6 h and 200 °C for 12 h, were selected for further studies using SEM and MBC. The interaction of AgNPs and microorganisms was shown using SEM. The result indicated the cell membrane changed when contacted with the nanoparticles (Fig. 5). This was particularly true for gram-negative bacteria, showing a thin layer of membrane and having pores. Subsequently, MBC of the bacterial concentration at  $10^8$  CFU/ml was determined for both *S. epidermidis* and *P. aeruginosa*. This demonstrated the lowest concentration of nanoparticles with bactericidal effect was 0.01 mg/mL for AgNPs fabricated at 100 °C for 6 h and 200 °C for 12 h against  $10^8$  CFU/ml *S. epidermidis*. The corresponding concentrations was 0.0025 mg/mL for AgNPs fabricated at 100 °C for 6 h and 0.00125 mg/mL for those formed at 200 °C for 12 h against  $10^8$  CFU/ml *P. aeruginosa*. Moreover, the microbicidal activity of nanoparticles provided high efficiency within 2 months. At the lower AgNPs concentrations, clearly there was an effect on the lethality against gram negative-bacteria whereas higher concentrations were needed to control gram-positive bacteria.

### Cytotoxicity Evaluation

To determine the cytotoxicity of AgNPs@AV on human cells, PBMCs were tested using the MTT assay. The result was calculated as %survival of the cells cultured with samples at concentrations of 0.04, 0.02, 0.01, 0.005, and 0.0025 mg/mL of 100 °C for 6 h and 200 °C for 12 h processed AgNPs@AV. The %survival of the cells in less 0.0025 mg/mL of both nanoparticles was significantly higher than 50% which confirms that these AgNPs@AVs were non-toxic to human PBMCs. Nanoparticles produced by green synthesis can be useful in biomedical applications.

232

## 233 Discussion

234 Recently, there has been increasing study of AgNPs synthesis to develop several applications such  
 235 as catalysis, biosensing, imaging, and antibacterial activity. Green synthesis is an alternative  
 236 method developed to produce metal nanoparticles by using natural compounds or plant  
 237 components. These are environmentally friendly processes that avoid the toxicity of chemicals.  
 238 Algae, bacteria, fungi and plants have been used to synthesize NPs without the need for additional  
 239 reducing and stabilizing agents. Plant extracts contain functional substances, including cyclic  
 240 peptides, sorbic acid, citric acid, euphol, polyhydroxy limonoids, ascorbic acid, retinoic acid,  
 241 tannins, ellagic acid, and gallic acid, among others, are strongly believed to play a crucial role in  
 242 the bioreduction and stabilization of nanoparticles (*Rajan et al., 2015*). These processes seem  
 243 facile, safe, low cost, and ecofriendly, eliminating the elaborate process of maintaining aseptic cell  
 244 cultures and are suitable for large scale production. Therefore, this study focused on the  
 245 biosynthesis of AgNPs with plant extracts of aloe vera leaves. Zhang et al. (2010) speculated that  
 246 the hydroquinones in the aloe vera plant extract act as the reducing agents. Additionally, the  
 247 spherical shape of AgNPs was governed by the weaker binding of proteins in the solution leading  
 248 to the isotropic growth of the AgNPs. Here, the hydrothermal process was applied to AgNPs  
 249 synthesis in which time and temperature had an effect on the resulting crystalline structure of  
 250 AgNPs. High temperature and pressure are necessary to facilitate the reduction processes (*Liu et*  
 251 *al., 2012*). Nucleation and the growth of AgNPs depend on the reaction temperature. Additionally,  
 252 capping agents also play a role in the synthesis of nanoparticles. Selective interaction of capping  
 253 agents may lead to anisotropic crystalline growth. Poly (vinyl) pyrrolidone is widely used to  
 254 synthesize nanorods due to their preferential interaction with the (100) plane (*Pal, Tak & Song,*

2007). In the case of aloe vera, a (111) plane of AgNPs predominantly arose as a major peak. This plane was reported responsible for a strong antibacterial effect (Feng et al., 2000).

The factors controlling the morphology, size, and product purity in the hydrothermal process were reaction temperature and time (Byrappa & Adschiri, 2007; Liu et al., 2014). Moreover, biosynthesis of inorganic nanoparticles with the plant extracts improved their bactericidal effect (Yousefzadi, Rahimi & Ghafari, 2014). High bactericidal activity was possibly caused by synergistic antibacterial effects of AgNPs and naturally-occurring chemicals in aloe vera. The lethal mechanism against pathogenic *S. epidermidis* and *P. aeruginosa* might involve the release of Ag<sup>+</sup> ions from AgNPs and the formation of crystalline bio-organic compounds of aloe vera plant extract assembled with AgNPs anchored onto the bacterial cell walls, producing pits and penetrating into the cytoplasm. Various natural ligands can interact with microbial membrane such as saponin, tannin, terpenoids, and flavonoids in the aloe vera (Griffin et al., 1999; Sahu et al., 2013). The interaction with the cell membrane may increase its permeability leading to cell lysis. Moreover the free radicals from metal result in induction of oxidative stresses, such as reactive oxygen species (ROS), that can damage the bacterial membranes, mitochondria, and DNA. This eventually results in the death of the cell (Hajipour et al., 2012; Tamboli & Lee, 2014). From our results, a schematic mechanism involving the reaction of AgNPs@AV to kill the bacteria was purposed and illustrated in Figure 6. Additionally, the susceptibility of different types of bacteria was attributed to the structure of their bacterial cell walls. Previous studies indicated that the silver ion released from AgNPs was responsible for antibacterial activity (Feng et al., 2000). The free silver ion can then bind with the thiol groups of enzymes (Zhang et al., 2013). The AgNPs formed at 100 °C for 6 h were found to be toxic to both gram-positive and gram-negative bacteria. This might due to the smaller size of the AgNPs fabricated under these conditions which results a higher

surface area (Cui *et al.*, 2013). Silver ion release is a size dependent process (Cui *et al.*, 2013). The antibacterial activity of the synthesized AgNPs might be due to the silver ion release and the resulting genotoxic activity of aloe vera on *E. coli* (Zhang *et al.*, 2010). Interestingly, the samples processed at 200 °C for 12 h had the largest size of those examined and they provided effective growth inhibition of the pathogens. The results indicated that the larger AgNPs might contain high levels of incorporated aloe vera compounds as well as a pure Ag phase due their long time and high temperature treatment. Therefore, this hybrid nanostructure formed under specific conditions can potential be an antibacterial agent.

## Conclusion

This report described a green and facile method to synthesize AgNPs in large quantities. Silver nitrate was reduced in an aloe vera plant-extract solution under a hydrothermal condition. Aloe vera plant extract solutions were used as both reducing and stabilizing agents. Fine spherically shape nanoparticles were obtained. The particle size of AgNPs can be tuned by varying the hydrothermal temperature. The antibacterial effect of AgNPs@AV showed promise for use as a highly potent agent with minimal cytotoxicity to human PBMCs. These hybrid nanomaterials could potentially be used in biomedical applications.

## Acknowledgment

The authors acknowledge the National Research University Project of Thailand, Office of the Higher Education Commission, through the Advanced Functional Materials Cluster of Khon Kaen University.

## References:

- 302 **Anker JN, Hall WP, Lyandres O, Shah NC, Zhao J, Van Duyne RP. 2008.** Biosensing with  
303 plasmonic nanosensors. *Nature materials* **7**,442-453.
- 304 **Byrappa K, Adschiri T. 2007.** Hydrothermal technology for nanotechnology. *Progress in Crystal*  
305 *Growth and Characterization of Materials* **53**,117-166.
- 306 **Chandran SP, Chaudhary M, Pasricha R, Ahmad A, Sastry M. 2006.** Synthesis of gold  
307 nanotriangles and silver nanoparticles using Aloe vera plant extract. *Biotechnology*  
308 *progress* **22**,577-583.
- 309 **Cho K-H, Park J-E, Osaka T, Park S-G. 2005.** The study of antimicrobial activity and  
310 preservative effects of nanosilver ingredient. *Electrochimica Acta* **51**,956-960.
- 311 **Chudasama B, Vala AK, Andhariya N, Mehta R, Upadhyay R. 2010.** Highly bacterial resistant  
312 silver nanoparticles: synthesis and antibacterial activities. *Journal of Nanoparticle*  
313 *Research* **12**,1677-1685.
- 314 **Cui L, Chen P, Chen S, Yuan Z, Yu C, Ren B, Zhang K. 2013.** In situ study of the antibacterial  
315 activity and mechanism of action of silver nanoparticles by surface-enhanced Raman  
316 spectroscopy. *Analytical chemistry* **85**,5436-5443.
- 317 **Emaga TH, Robert C, Ronkart SN, Wathelet B, Paquot M. 2008.** Dietary fibre components  
318 and pectin chemical features of peels during ripening in banana and plantain varieties.  
319 *Bioresource Technology* **99**,4346-4354.
- 320 **Feng Q, Wu J, Chen G, Cui F, Kim T, Kim J. 2000.** A mechanistic study of the antibacterial  
321 effect of silver ions on Escherichia coli and Staphylococcus aureus. *Journal of biomedical*  
322 *materials research* **52**,662-668.



- Griffin SG, Wyllie SG, Markham JL, Leach DN. 1999. The role of structure and molecular properties of terpenoids in determining their antimicrobial activity. *Flavour and Fragrance Journal* **14**,322-332.
- Hajipour MJ, Fromm KM, Ashkarran AA, de Aberasturi DJ, de Larramendi IR, Rojo T, Serpooshan V, Parak WJ, Mahmoudi M. 2012. Antibacterial properties of nanoparticles. *Trends in biotechnology* **30**,499-511.
- Lee G-J, Shin S-I, Kim Y-C, Oh S-G. 2004. Preparation of silver nanorods through the control of temperature and pH of reaction medium. *Materials Chemistry and Physics* **84**,197-204.
- Lee K-S, El-Sayed MA. 2006. Gold and silver nanoparticles in sensing and imaging: sensitivity of plasmon response to size, shape, and metal composition. *The Journal of Physical Chemistry B* **110**,19220-19225.
- Livermore DM. 2002. Multiple mechanisms of antimicrobial resistance in *Pseudomonas aeruginosa*: our worst nightmare? *Clin Infect Dis* **34**(5),634-40.
- Liu J, Sonshine DA, Shervani S, Hurt RH. 2010. Controlled release of biologically active silver from nanosilver surfaces. *ACS nano* **4**,6903-6913.
- Liu Z, Wang Y, Zu Y, Fu Y, Li N, Guo N, Liu R, Zhang Y. 2014. Synthesis of polyethylenimine (PEI) functionalized silver nanoparticles by a hydrothermal method and their antibacterial activity study. *Materials Science and Engineering: C* **42**,31-37.
- Liu Z, Xing Z, Zu Y, Tan S, Zhao L, Zhou Z, Sun T. 2012. Synthesis and characterization of L-histidine capped silver nanoparticles. *Materials Science and Engineering: C* **32**,811-816.
- Morones JR, Elechiguerra JL, Camacho A, Holt K, Kouri JB, Ramirez JT, Yacaman MJ. 2005. The bactericidal effect of silver nanoparticles. *Nanotechnology* **16**,2346.

- Nabikhan A, Kandasamy K, Raj A, Alikunhi NM. 2010.** Synthesis of antimicrobial silver nanoparticles by callus and leaf extracts from saltmarsh plant, *Sesuvium portulacastrum* L. *Colloids and Surfaces B: Biointerfaces* **79**,488-493.
- Otto M. 2009.** *Staphylococcus epidermidis* – the “accidental” pathogen. *Nat Rev Microbiol* **7(8)**,555–567.
- Pal S, Tak YK, Song JM. 2007.** Does the antibacterial activity of silver nanoparticles depend on the shape of the nanoparticle? A study of the gram-negative bacterium *Escherichia coli*. *Applied and environmental microbiology* **73**,1712-1720.
- Pradhan N, Pal A, Pal T. 2002.** Silver nanoparticle catalyzed reduction of aromatic nitro compounds. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* **196**,247-257.
- Rai M, Deshmukh S, Ingle A, Gade A. 2012.** Silver nanoparticles: the powerful nanoweapon against multidrug resistant bacteria. *Journal of applied microbiology* **112**,841-852.
- Rai M, Yadav A, Gade A. 2009.** Silver nanoparticles as a new generation of antimicrobials. *Biotechnology advances* **27**,76-83.
- Rajan R, Chandran K, Harper SL, Yun S-I, Kalaichelvan PT. 2015.** Plant extract synthesized silver nanoparticles: An ongoing source of novel biocompatible materials. *Industrial Crops and Products* **70**,356-373.
- Reynolds T, Dweck A. 1999.** Aloe vera leaf gel: a review update. *Journal of ethnopharmacology* **68**,3-37.
- Sahu PK, Giri DD, Singh R, Pandey P, Gupta S, Shrivastava AK, Kumar A, Pandey KD. 2013.** Therapeutic and medicinal uses of Aloe vera: a review. *Pharmacology & Pharmacy* **4**,599.


- 368 **Sharma VK, Yngard RA, Lin Y. 2009.** Silver nanoparticles: green synthesis and their  
369 antimicrobial activities. *Advances in colloid and interface science* **145**,83-96.
- 370 **Sun Q, Cai X, Li J, Zheng M, Chen Z, Yu C-P. 2014.** Green synthesis of silver nanoparticles  
371 using tea leaf extract and evaluation of their stability and antibacterial activity. *Colloids*  
372 *and Surfaces A: Physicochemical and Engineering Aspects* **444**,226-231.
- 373 **Sun Y, Mayers B, Xia Y. 2003.** Transformation of silver nanospheres into nanobelts and  
374 triangular nanoplates through a thermal process. *Nano Letters* **3**,675-679.
- 375 **Sun Y, Xia Y. 2002.** Shape-controlled synthesis of gold and silver nanoparticles. *Science*  
376 **298**,2176-2179.
- 377 **Taleb A, Petit C, Pileni M. 1997.** Synthesis of highly monodisperse silver nanoparticles from  
378 AOT reverse micelles: a way to 2D and 3D self-organization. *Chemistry of Materials*  
379 **9**,950-959.
- 380 **Tamboli DP, Lee DS. 2014.** Mechanistic antimicrobial approach of extracellularly synthesized  
381 silver nanoparticles against gram positive and gram negative bacteria. *Journal of*  
382 *hazardous materials* **260**,878-884.
- 383 **Vazquez B, Avila G, Segura D, Escalante B. 1996.** Antiinflammatory activity of extracts from  
384 Aloe vera gel. *Journal of ethnopharmacology* **55**,69-75.
- 385 **Yousefzadi M, Rahimi Z, Ghafari V. 2014.** The green synthesis, characterization and  
386 antimicrobial activities of silver nanoparticles synthesized from green alga *Enteromorpha*  
387 *flexuosa* (Wulfen) J. Agardh. *Materials Letters* **137**,1-4.
- 388 **Zhang Y, Cheng X, Zhang Y, Xue X, Fu Y. 2013.** Biosynthesis of silver nanoparticles at room  
389 temperature using aqueous aloe leaf extract and antibacterial properties. *Colloids and*  
390 *Surfaces A: Physicochemical and Engineering Aspects* **423**,63-68.

391 **Zhang Y, Yang D, Kong Y, Wang X, Pandoli O, Gao G. 2010.** Synergetic antibacterial effects  
 392 of silver nanoparticles@ aloe vera prepared via a green method. *Nano Biomed Eng* **2**,252-  
 393 257.


394 **Zhang Z, Patel RC, Kothari R, Johnson CP, Friberg SE, Aikens PA. 2000.** Stable silver  
 395 clusters and nanoparticles prepared in polyacrylate and inverse micellar solutions. *The*  
 396 *Journal of Physical Chemistry B* **104**,1176-1182.

397


398 LIST OF FIGURES AND LEGENDS

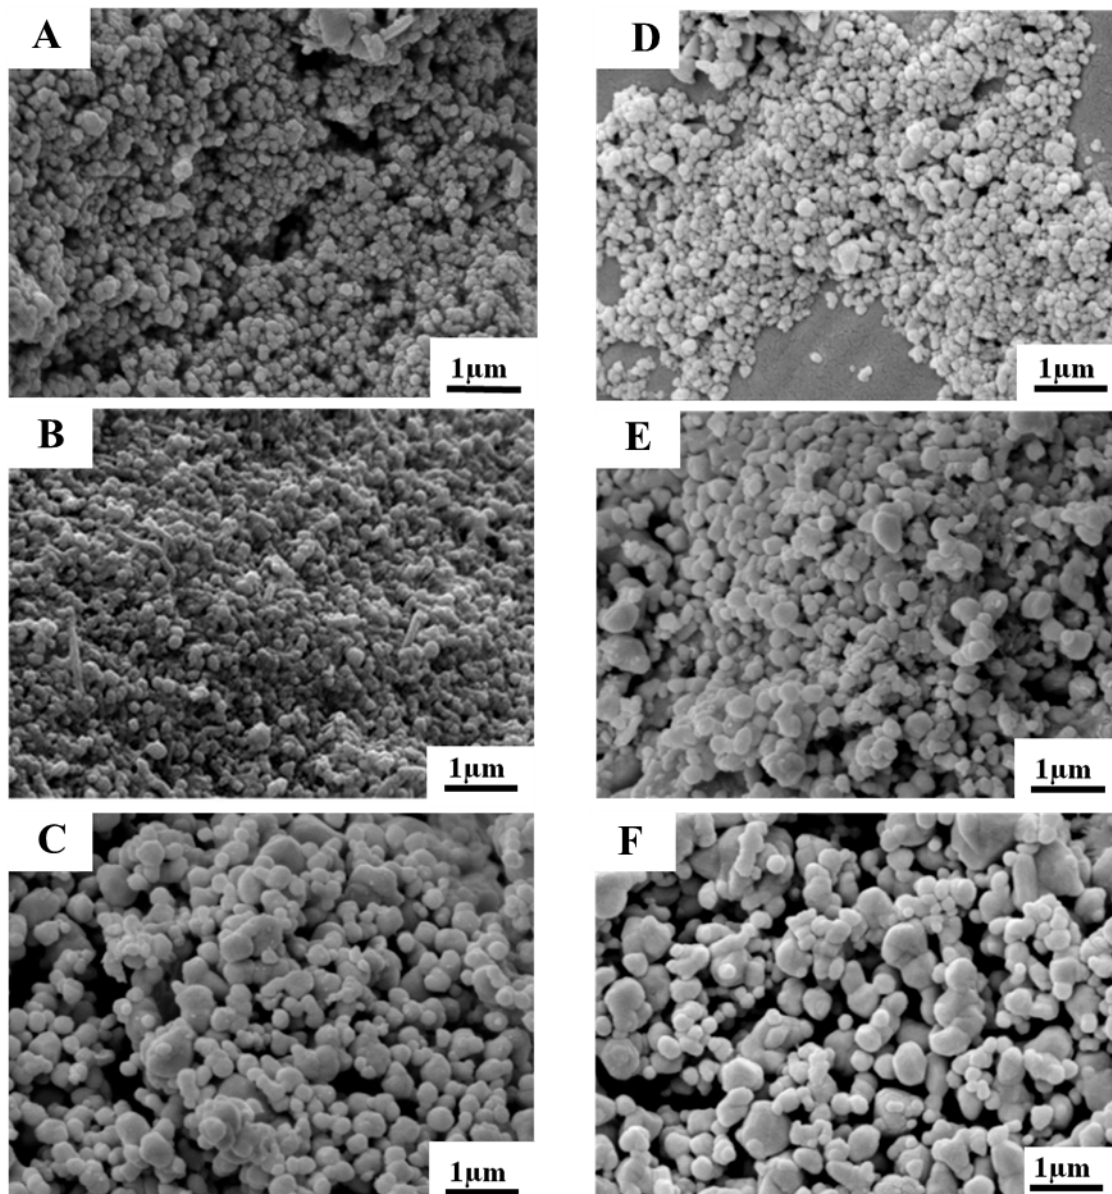


399  
 400 **Figure 1 SEM images of silver nanoparticles on a glass slide after incubation at different**  
 401 **temperature and time combinations.** SEM images of AgNPs were obtained at (A) 100 °C for  
 402 6 h, (B) 150 °C for 6 h, (C) 200 °C for 6 h, (D) 100 °C for 12 h, (E) 150 °C for 12 h and (F) 200  
 403 °C for 12 h.

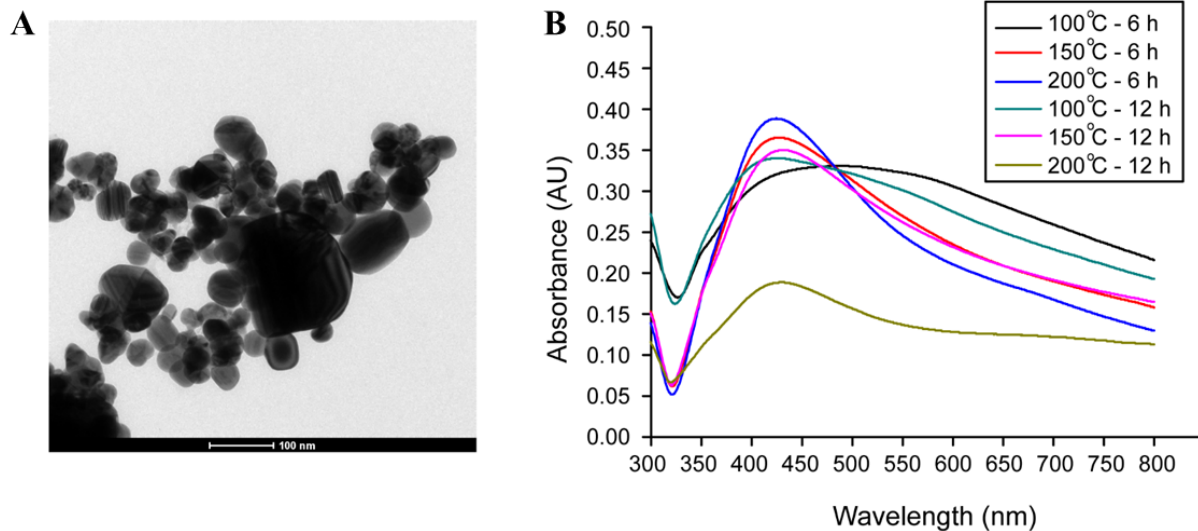

**Figure 2 TEM image and UV-vis absorption spectra of AgNPs synthesized using an aloe vera plant-extract solution.** TEM image of AgNPs was obtained at 100 °C for 6 h (A) and UV-vis absorption spectra of AgNPs were shown in the maximum absorption at 420 nm (B).

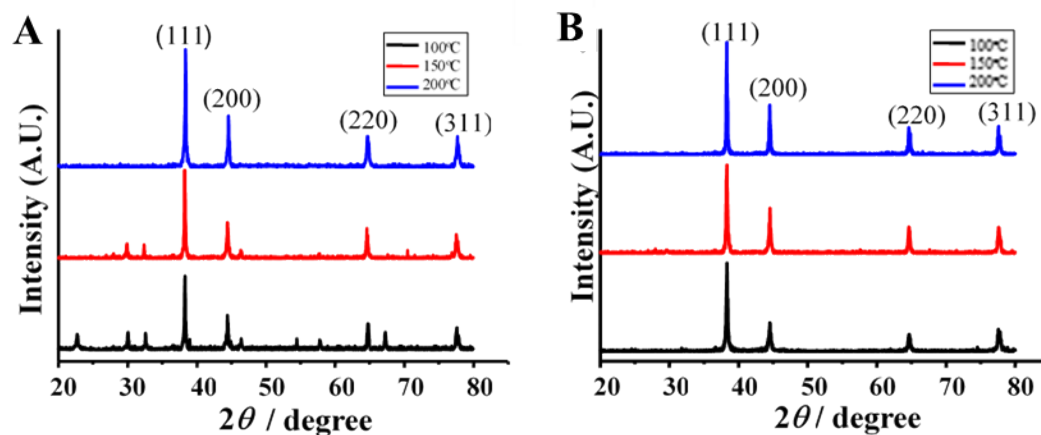

**Figure 3 XRD patterns of AgNPs synthesized using an aloe vera plant-extract solution.** The AgNPs were prepared at temperatures of 100, 150, and 200 °C and for different times (A) 6 h and (B) 12 h.

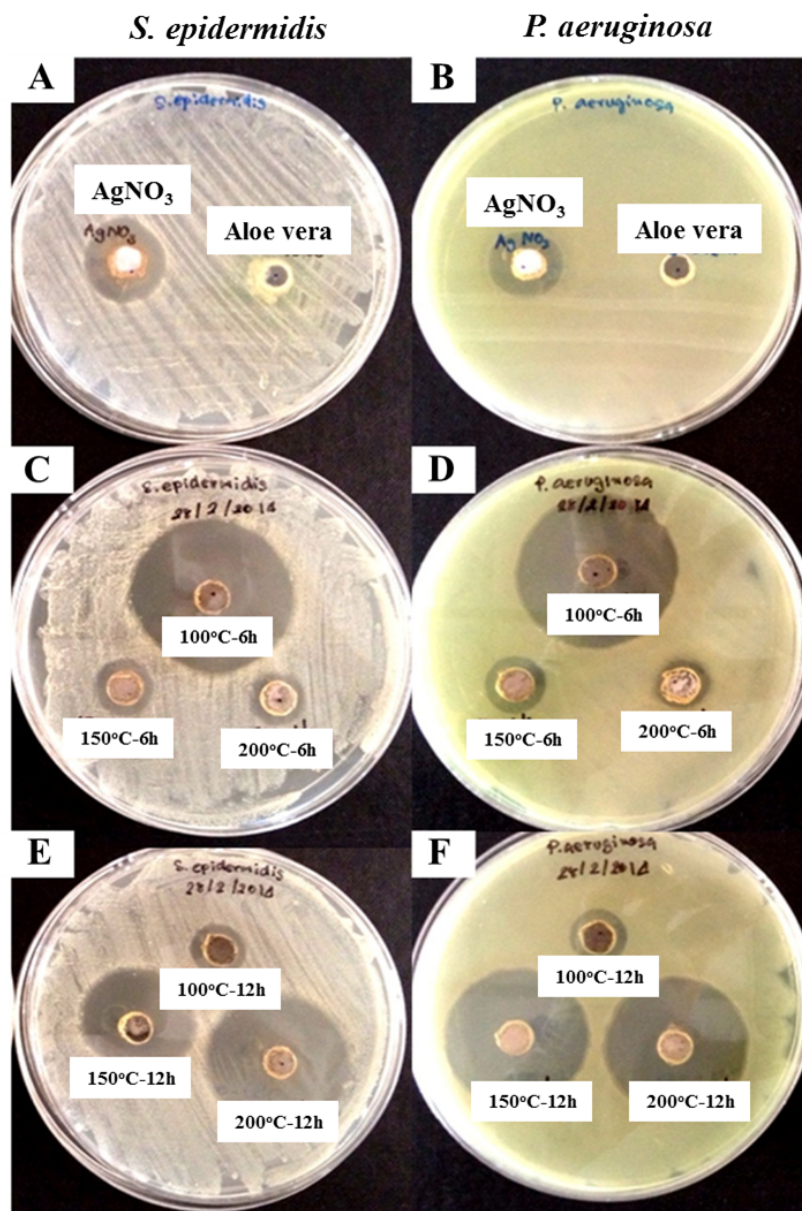


**Figure 4** Antibacterial activity assay of AgNPs against *S. epidermidis* and *P. aeruginosa*. (A) AgNO<sub>3</sub> and aloe-vera extract control in *S. epidermidis*, (B) AgNO<sub>3</sub> and aloe-vera extract control in *P. aeruginosa*, (C) 100 °C-6 h, 150 °C-6 h, and 200 °C-6 h AgNPs at (0.1 mg/mL) in *S. epidermidis*, (D) 100 °C-6 h, 150 °C-6 h, and 200 °C-6 h AgNPs at (0.1 mg/mL) in *P. aeruginosa*, (E) 100 °C-12 h, 150 °C-12 h, and 200 °C-12 h AgNPs at (0.1 mg/mL) in



471 *S. epidermidis*, (F) 100 °C-12 h, 150 °C-12 h, and 200 °C-12 h AgNPs at (0.1 mg/mL) in  
 472 *P. aeruginosa*.

473

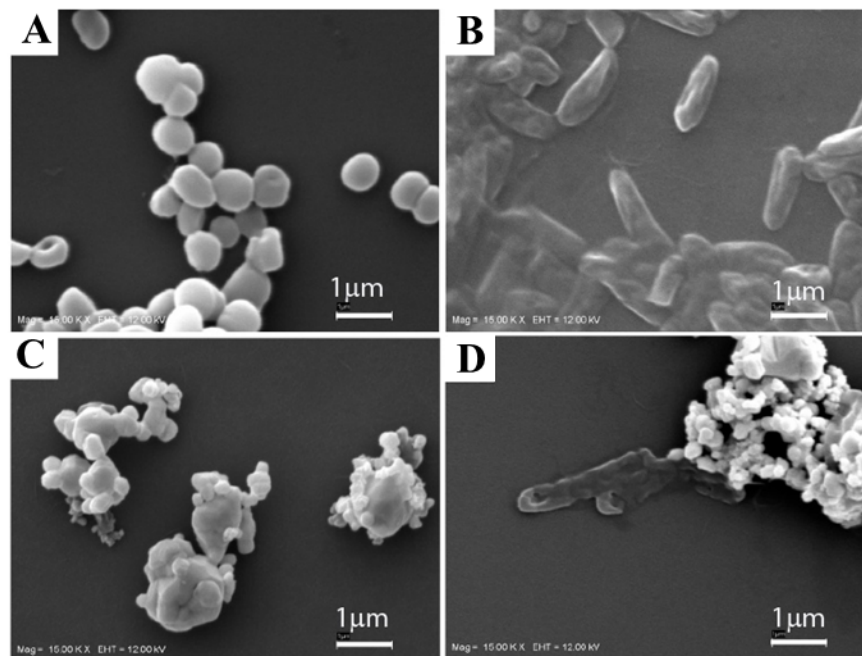

474

475

476 **Figure 5 SEM images of the bacterial strains. (A) *S. epidermidis*, (B) *P. aeruginosa*,**

477 **(C) *S. epidermidis* treated with 100-6 h AgNPs (0.04 mg/mL), (D) *P. aeruginosa* treated with**

478 **100-6 h AgNPs (0.04 mg/mL).**

479

480

481

482

483

484

485

486

487

488


489

490

491

492

493

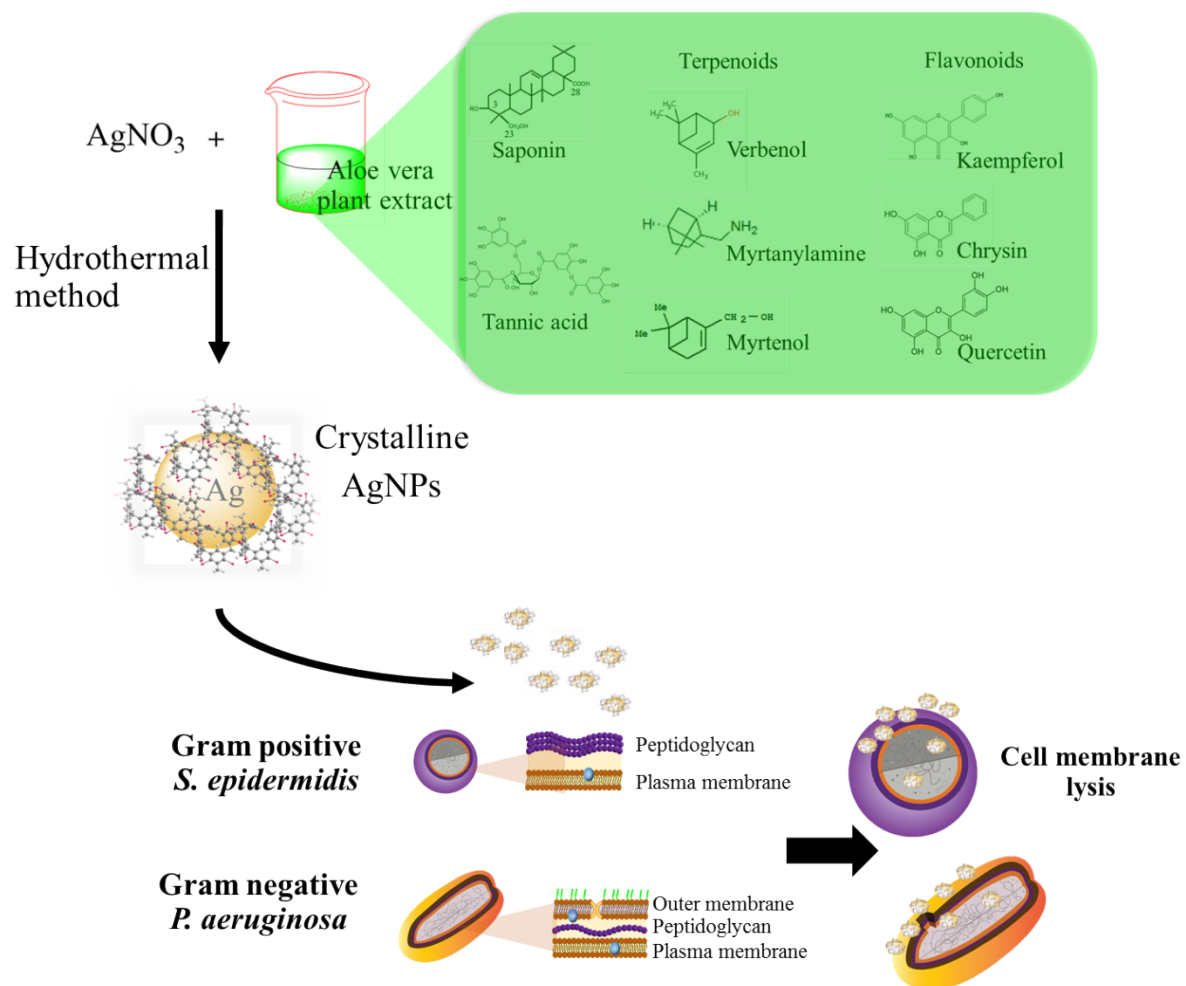

502  
503 **Figure 6 Illustration of proposed bacterial inactivation mechanism that may involve**  
504 **nanocrystalline AgNPs@AV to disrupt the bacterial membrane.** In the hydrothermal method,  
505 various organic compounds such as saponin, tannin, terpenoids, and flavonoids in the aloe vera  
506 plant extract can be combined with  $\text{AgNO}_3$  synthesizing AgNPs@AV. These nanocrystals may

507 accumulate at the cell membrane increasing its permeability, which eventually results in the death  
 508 of *P. aeruginosa* and *S. epidermidis*.

509

510

511 LIST OF TABLE CAPTIONS

512 Table 1 Sizes of AgNPs and antibacterial efficiency of AgNPs in different hydrothermal  
513 processes.

AgNPs samples	Inhibition zone diameter (cm)		
	Size of AgNPs (nm)	<i>S. epidermidis</i> (gram positive bacteria)	<i>P. aeruginosa</i> (gram negative bacteria)
100 °C - 6 h	70.70±22	3.65 ± 0.50*	3.90 ± 0.42*
150 °C - 6 h	79.47±22	1.70 ± 0.43	1.60 ± 0.28
200 °C - 6 h	161.66±53	1.50 ± 0.42	1.40 ± 0.32
100 °C - 12 h	95.25±23	1.72 ± 0.42	1.44 ± 0.29
150 °C - 12 h	149.55±47	3.60 ± 0.56*	3.15 ± 0.49*
200 °C - 12 h	192.02±53	3.90 ± 0.84*	3.45 ± 0.21*

514  
515 \* $p < 0.01$  compared with an AgNO<sub>3</sub> control

516  
517  
518  
519  
520  
521  
522  
523  
524  
525  
526  
527  
528  
529  
530  
531  
532  
533  
534  
535  
536  
537  
538

539  
540  
541